

Coordination polymerization of ethylene in water by Pd(II) and Ni(II) catalysts

Anke Held, Florian M. Bauers and Stefan Mecking*

Institut für Makromolekulare Chemie und Freiburger Materialforschungszentrum der Albert-Ludwigs-Universität Freiburg, Stefan-Meier-Str. 31, D-79104 Freiburg, Germany. E-mail: mecking@ruf.uni-freiburg.de

Ethylene is polymerized in water as a reaction medium by Pd(II) and Ni(II) complexes to afford branched or linear homopolymer.

Water possesses unique properties as a reaction medium. It is highly polar and immiscible with most organic compounds, has a high heat capacity and also features a strong propensity for micelle formation. In addition, water is an ideal medium from an environmental and safety perspective. Thus, emulsion and suspension polymerization of olefinic monomers is employed on a vast scale, e.g. for the direct production of water-based lattices, used for coatings and paints. In contrast to these free radical polymerizations, transition metal catalyzed coordination polymerization reactions in water have received less attention, as the early transition metal catalysts¹ used predominately are extremely sensitive to moisture.


Late transition metal complexes are generally less sensitive to polar media due to their less oxophilic nature. Due to the propensity of late transition metal alkyl complexes for β -hydride elimination, dimers or oligomers are usually obtained in C–C linkage of ethylene.² Only a limited number of catalysts for polymerization to high molecular weight products are known. Most of them are based either on neutral Ni(II) complexes^{3,14a} of formally monoanionic bidentate ligands or on cationic Fe, Co, Ni or Pd complexes⁴ of neutral multidentate ligands with bulky substituted N donor atoms.⁵ The aforementioned stability of late transition metal complexes is demonstrated by the tolerance of some of these polymerization catalysts towards polar functionalized comonomers^{3d,4b,c} and polar organic solvents.^{3c,d,4c,6}

In the context of possible side reactions in transition metal catalysis in aqueous media⁷ (such as hydrolysis of metal alkyl species, attack of water on coordinated substrates or coordination of water to the metal center as a ligand), regarding polymerization reactions a conceivable effect of water on chain transfer⁸ is of specific interest as small (absolute) changes in the

overall chain transfer rate will strongly influence product molecular weight.

A very slow (ca. 1 turnover per day) coordination polymerization of ethylene in water catalyzed by a Rh complex has previously been investigated.⁹ We now report on the homopolymerization of ethylene in water by neutral Ni(II) and cationic Pd(II) complexes.

Exposure of an aqueous suspension of Pd complex **1**^{4c} to ethylene at elevated pressure results in formation of high molecular weight, highly branched polyethylene (Table 1). The reaction is effective under mild conditions (7 bar, room temperature), an increase of the ethylene pressure to 40 bar resulting in a doubling of productivity (entry 1 vs. 3). Comparison of 3 and 16 h experiments reveals no significant deactivation of the cationic catalyst in the presence of water (entry 2 vs. 3). In comparison to polymerization employing a homogeneous solution of **1** in CH₂Cl₂ as a non-aqueous solvent

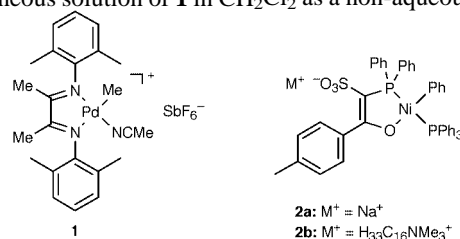

(entry 3 vs. 4), activities are similar. However, branching is reduced in comparison to reaction in CH₂Cl₂ (69 to 83 branches per 1000 C atoms in runs 1 to 3 vs. 109 branches per 1000 C in run 4; determined by ¹H NMR). Also, GPC analysis reveals a much higher molecular weight of the polymers obtained in water (Table 1). These findings correspond to the physical appearance of the polymers: whereas the material obtained in CH₂Cl₂ is a highly viscous oil, the polymers obtained in the aqueous reaction medium are rubbery solids. In preliminary

Table 1 Polymerization results

Entry No.	Reaction conditions			Results						
	Catalyst	n(cat.)/ μmol	Ethylene pressure/bar Reaction medium	Reaction time/h	Polymer yield/g	Productivity/ mol(ethylene) mol(cat.) ⁻¹	Average activity/ mol(ethylene) mol(cat.) ⁻¹ h ⁻¹	M _w ^a /g mol ⁻¹	M _n ^a /g mol ⁻¹ (M _w /M _n)	
1	1	81	7 H ₂ O	23	7.4	3 260	140	160 000	70 600 (2.3)	
2	1	61	40 H ₂ O	3	2.3	1 340	450	181 100	63 500 (2.8)	
3	1	61	40 H ₂ O	16	10.9	6 380	400	179 400	77 700 (2.3)	
4	1	61	50 CH ₂ Cl ₂	14	14.4	8 430	600	32 300	14 500 (2.2)	
5	2a^b	130	50 acetone:H ₂ O 50:50	1.5	2.5	680	450	^c	^c	
6	2a^b	121	50 acetone:H ₂ O 50:50	3	3.2	940	310	^c	^c	
7	2a^b	108	50 acetone:H ₂ O 5:95	2	2.2	710	360	2 230	970 (2.3)	
8	2a^b	89	50 toluene:H ₂ O 5:95	2	5.9	2 360	1 180	3 030	960 (3.1)	
9	2b^b	116	50 toluene:H ₂ O 5:95	1.5	1.0	310	210	^c	^c	
10	2b^b	104	50 toluene:H ₂ O 5:95	3	1.6	550	180	^c	^c	
11	2a^b	12	50 toluene	2	9.0	26 680	13 340	580 000	13 900 (42)	
12	2a^b	26	50 acetone	2	22.2	30 440 ^d	15 220 ^d	94 000	3 770 (25)	
13	2b^b	9	50 toluene	1.75	5.2	20 600	11 780	28 800	5 440 (5.3)	

Reaction temperature: room temp. (entries 1 to 4), 70 °C (entries 5 to 13). Total volume of water and/or organic solvent: 100 mL.

^a Determined vs. polystyrene (entry 1 to 4) resp. linear polyethylene (entry 5 to 13) standards. ^b Phosphine scavenger [Rh(CH₂=CH₂)₂(acac)] (Ni:Rh 2:1). ^c Not determined. ^d Probably mass transfer limited.

experiments, the water ligand of the cationic complex $[(\text{ArN}=\text{C}(\text{Me})\text{C}(\text{Me})=\text{NAr})\text{PdMe}(\text{OH}_2)]^+\text{SbF}_6^-$ ($\text{Ar} = 2,6\text{-Pr}_2\text{C}_6\text{H}_3$)¹⁰ was found to be displaced completely upon addition of ethylene in low temperature NMR experiments. This result implies that in catalysis in aqueous media with cationic complexes of this type no severe blocking of coordination sites by water should be expected, in accordance with the above polymerization experiments.

In ethylene polymerisation by a neutral Ni(II) complex with a P,O ligand, introduction of a sulfonate substituent has been reported to enhance formation of higher molecular weight products (toluene as reaction medium).^{3c,d} At the same time, the sulfonate group affects water solubility. In order to produce higher molecular weight polymer the absence of strongly coordinating phosphine ligands is required.^{3d,11} For this reason we have employed complex **2a**,^{12,13} utilizing $[\text{Rh}(\text{H}_2\text{C}=\text{CH}_2)_2(\text{acac})]$ as a phosphine scavenger. For comparison to water-soluble **2a** with respect to aqueous polymerization in the presence of a water-immiscible solvent (*vide infra*) the novel complex **2b** was prepared by oxidative addition of $4\text{-MeC}_6\text{H}_4\text{C}(\text{O})\text{C}(\text{SO}_3^-\text{H}_{33}\text{C}_{16}\text{NMe}_3^+)=\text{PPh}_3$ to $[\text{Ni}(\text{cod})_2]$ in the presence of PPh_3 , or by addition to $[\text{Ni}(\text{PPh}_3)_4]$.¹³ Introduction of the large $\text{H}_{33}\text{C}_{16}\text{NMe}_3^+$ cation results in a strong increase in lipophilicity: whereas **2a** dissolves in the aqueous phase upon addition of water to a toluene solution of the complex, **2b** remains in the organic phase.

The stability of C–C linkage catalysts based on Ni complexes with anionic bidentate ligands towards protic media, including water, had been noted early on by the original inventors.¹⁴ However, successful polymerization to afford higher molecular weight products in water has not been reported, to the best of our knowledge. The complex $[\{\kappa^2\text{P},\text{O}-\text{Ph}_2\text{PC}(\text{Ph})=\text{C}(\text{OEt})\text{O}\}\text{NiPh}(\text{PEt}_3)]$ (removal of PEt_3 by phosphine scavengers) was reported to be completely inactive for ethylene polymerization in organic media in the presence of 1000 eq. water.^{3d,15} For this reason, we were somewhat surprised to observe formation of linear polyethylenes employing catalysts **2a** and **2b** in an aqueous environment, utilizing only a small amount of water-miscible (acetone) or -immiscible (toluene) organic solvent to enable injection of the phosphine scavenger or the scavenger and **2b**, respectively (Table 1, entries 7 to 10). By comparison to polymerization in neat toluene or acetone¹⁶ (entries 11 to 13), polymer molecular weight is significantly reduced and productivity is lowered in aqueous media. From the data presented, no dramatic effect of water on chain transfer reactions is evident, the lowering of polymer molecular weight also being attributable to a slower chain growth (as reflected by the lower productivity) caused by the lower solubility of ethylene in water. Considering catalyst stability, comparison of entries 5 vs. 6 and 9 vs. 10 shows that the catalysts are still active for polymerization after several hours in water. A preliminary comparison of the hydrophilic **2a** and the lipophilic **2b** in the multiphase system water/toluene/insoluble polymer (entries 8 and 9) reveals that phosphine abstraction from **2a** is not significantly hampered by the different solubilities of **2a** and $[\text{Rh}(\text{H}_2\text{C}=\text{CH}_2)_2(\text{acac})]$.

Interestingly, when performing the Ni(II)-catalyzed polymerization in the presence of ionic or non-ionic surfactants (SDS, Triton X-100), stable polyethylene emulsions are obtained. Typically, emulsions with particle sizes in the range of ϕ 80 to 300 nm are obtained at a catalyst productivity of, e.g. 1300 mol(ethylene) per mol(Ni) (conditions of run 7, surfactant added).

In conclusion, high molecular weight polymers can result from the coordination polymerization of ethylene in water at high catalyst activities. Branched or linear polymers are accessible in water as a reaction medium.

The authors thank R. Mülhaupt for his interest in our work. Financial support by BASF AG is gratefully acknowledged, and we thank B. Manders and M. O. Kristen for valuable discussions. A.H. thanks the Deutsche Forschungsgemeinschaft for a Graduiertenkolleg stipend. A generous loan of PdCl_2 was provided by Degussa-Huels AG. GPC analyses of linear

polyethylenes were carried out by D. Lilje (BASF) and ³¹P NMR analyses were provided by D. Hunkler (Freiburg).

Notes and references

- Ziegler Catalysts, ed. G. Fink, R. Mülhaupt and H. H. Brintzinger, Springer, Berlin, 1995.
- G. Wilke, *Angew. Chem., Int. Ed. Engl.*, 1988, **27**, 185; *Angew. Chem.*, 1988, **100**, 189. M. Peuckert and W. Keim, *Organometallics*, 1983, **2**, 594.
- (a) W. Keim, R. Appel, A. Storeck, C. Krueger and R. Goddard, *Angew. Chem., Int. Ed. Engl.*, 1981, **20**, 116; *Angew. Chem.*, 1981, **93**, 91. (b) W. Keim, F. H. Kowaldt, R. Goddard and C. Krueger, *Angew. Chem., Int. Ed. Engl.*, 1978, **17**, 466; *Angew. Chem.*, 1978, **90**, 493. (c) K. A. Ostoja-Starzewski and J. Witte, *Angew. Chem., Int. Ed. Engl.*, 1987, **26**, 63; *Angew. Chem.*, 1987, **99**, 76. (d) U. Klabunde and S. D. Ittel, *J. Mol. Catal.*, 1987, **41**, 123. (e) C. Wang, S. Friedrich, T. R. Younkin, R. T. Li, R. H. Grubbs, D. A. Bansleben and M. W. Day, *Organometallics*, 1998, **17**, 3149. (f) L. K. Johnson, A. M. A. Bennett, S. D. Ittel, L. Wang, A. Parthasarathy, E. Hauptman, R. D. Simpson, J. Feldman and E. B. Coughlin (DuPont), WO98/30609, 1998.
- Ni, Pd: (a) L. K. Johnson, C. M. Killian and M. Brookhart, *J. Am. Chem. Soc.*, 1995, **117**, 6414. (b) L. K. Johnson, S. Mecking and M. Brookhart, *J. Am. Chem. Soc.*, 1996, **118**, 267. (c) S. Mecking, L. K. Johnson, L. Wang and M. Brookhart, *J. Am. Chem. Soc.*, 1998, **120**, 888. (d) L. K. Johnson, C. M. Killian, S. D. Arthur, J. Feldman, E. McCord, S. J. McLain, K. A. Kreutzer, M. A. Bennett, E. B. Coughlin, S. D. Ittel, A. Parthasarathy, D. Tempel and M. Brookhart (UNC-Chapel Hill/DuPont) WO 96/23010, 1996. Co, Fe: (e) B. L. Small, M. Brookhart and A. M. A. Bennett, *J. Am. Chem. Soc.*, 1998, **120**, 4049. (f) G. J. P. Britovsek, V. Gibson, B. S. Kimberley, P. J. Maddox, S. J. McTavish, G. A. Solan, A. J. P. White and D. J. Williams, *Chem. Commun.*, 1998, 849.
- A much larger variety of ligands is applicable for the particular case of palladium-catalyzed alternating olefin-carbon monoxide copolymerization as the involvement of CO can reduce the propensity for chain transfer: E. Drent and P. H. M. Budzelaar, *Chem. Rev.*, 1996, **96**, 663; A. Sen, *Acc. Chem. Res.*, 1993, **26**, 303. Alternating olefin-CO copolymerization in aqueous media: Z. Jiang and A. Sen, *Macromolecules*, 1994, **27**, 7215; G. Verspui, G. Papadogianakis and R. A. Sheldon, *Chem. Commun.*, 1998, 401; C. Bianchini, H. Man Lee, A. Meli, S. Moneti, V. Patinec, G. Petrucci and F. Vizza, *Macromolecules*, 1999, **32**, 3859.
- Tolerance of the palladium diimine complexes towards moisture has previously been noted, ref. 4b,c.
- Aqueous-Phase Organometallic Chemistry*, ed. B. Cornils and W. A. Herrmann, Wiley-VCH, Weinheim, 1998.
- E.g. the presence of additional ligands can promote chain transfer reactions in ethylene oligomerization: W. Keim and F. H. Kowaldt, *Erdoel, Erdgas, Kohle/Compand.-Dtsch. Ges. Mineraloelwiss. Kohlechem.*, 1978, **78–79**, 453.
- L. Wang, R. S. Lu, R. Bau and T. C. Flood, *J. Am. Chem. Soc.*, 1993, **115**, 6999.
- ¹H NMR (CD_2Cl_2 , 300 MHz, -50°C): 7.4–7.0 (m, 6H, H_{ar}), 4.6 (s, 2H, OH_2), 2.90 and 2.86 (septet, 7 Hz, 2H, CHMe_2 and $\text{C}'\text{HMe}_2$), 2.18 [s, 6H, $\text{N}=\text{C}(\text{Me})\text{C}(\text{Me})=\text{N}$], 1.32, 1.26, 1.15 and 1.10 (d, 7 Hz, 6H; CHMeMe' and $\text{C}'\text{HMeMe}'$), 0.26 (s, 3H, PdMe).
- Formation of polyethylene employing a PPh_3 complex in hexane suspension cf. ref. 3b.
- D. L. Beach and J. J. Harrison (Gulf), *Eur. Pat.* A 52929, 1982.
- Characteristic NMR data (¹³C{¹H}, 75 MHz; ³¹P{¹H}, 202 MHz), ligands $4\text{-MeC}_6\text{H}_4\text{C}(\text{O})\text{C}(\text{SO}_3^-\text{M}^+)=\text{PPh}_3$, $\text{M}^+ = \text{H}_{33}\text{C}_{16}\text{NMe}_3^+$: NMR (CDCl_3), ¹³C: δ 188.5 [d, ²J(C,P) 6 Hz, C=O], 81.0 [d, ¹J(C,P) 104 Hz, C=P], 52.2 ($\text{H}_{33}\text{C}_{16}\text{NMe}_3^+$). ³¹P: δ 16.8. $\text{M}^+ = \text{Na}^+$: NMR (CDCl_3), ¹³C: δ 191.5 (C=O), 81.3 [d, ¹J(C,P) 113 Hz, C=P]. ³¹P: δ 16.7. **2b** NMR ($\text{toluene}-d_6$): δ 187.1 [dd, ²J(C,P) 23 Hz, ³J(C,P) 8 Hz, C=O], 104.7 [d, ¹J(C,P) 44 Hz; =C(SO_3^-)P], 52.7 ($\text{H}_{33}\text{C}_{16}\text{NMe}_3^+$). ³¹P (C_6D_6): δ 38.3 [d, ²J(P,P) 272 Hz, =C(SO_3^-)P], 21.0 [d, ²J(P,P) = 272 Hz, PPh_3]. **2a** NMR (C_6D_6), ¹³C: δ 187.9 (br, C=O), 101.2 [d, ¹J(C,P) 42 Hz, =C(SO_3^-)P]. ³¹P: δ 35.4 [d, ²J(P,P) 276 Hz, =C(SO_3^-)P], 21.0 [d, ²J(P,P) 276 Hz, PPh_3].
- (a) R. Bauer, H. Chung, G. Cannell, W. Keim and H. van Zwet (Shell), *US Pat.* 3637636, 1972. (b) R. Bauer, H. Chung, K. W. Barnett, P. W. Glockner and W. Keim (Shell), *US Pat.* 3686159, 1972.
- Polymerization in the presence of 'up to 100 eq.' of water/Ni for a neutral nickel complex with a chelating N,O-ligand has recently been claimed: D. A. Bansleben, S. Friedrich, T. R. Younkin, R. H. Grubbs, C. Wang and R. T. Li (W. R. Grace), WO 98/42664, 1998.
- The broad molecular weight distributions observed in entries 11 and 12 are in agreement with previous studies: ref. 3d.